



Characterization of CuCrO_2 Material Produced Using Sol-Gel Method

Syahrul Humaidi^{*1}, Delviya Amisha¹, and Agung Imaddudin²

¹Department of Physics, Faculty of Mathematics and Natural Sciences, Universitas Sumatera Utara, Jl. Bioteknologi No. 1, Medan 20155, North Sumatra, Indonesia

²Center for Advanced Materials Research, National Research and Innovation Agency-BRIN, Building 470, Puspiptek Serpong Area, South Tangerang, Indonesia

*Corresponding Author: syahrul1@usu.ac.id

ARTICLE INFO

Article history:

Received 04 February 2023

Revised 17 February 2023

Accepted 24 February 2023

Available online 28 February 2023

E-ISSN: 2656-0755

P-ISSN: 2656-0747

How to cite:

S. Humaidi, D. Amisha, A. Imaddudin, "Characterization of CuCrO_2 Material Produced Using Sol-Gel Method," Journal of Technomaterial Physics, vol. 5, no. 01, Feb. 2023, doi:10.32734/jotp.v5i1.9910.



This work is licensed under a Creative Commons Attribution-ShareAlike 4.0 International.

<http://doi.org/10.32734/jotp.v5i1.9910>

ABSTRACT

This study aimed to analyze CuCrO_2 material produced using the sol-gel method. The characterization used is X-ray Diffraction (XRD) and Scanning Electron Microscope-Energy Dispersive Spectroscopy (SEM-EDS). The sample was made by weighing the raw material and measuring the solution with a measuring cup according to stoichiometric calculations, then dissolving it, burning it, grinding it, calcining it, sintering it, forming it into pellets, and re-sintering it. The XRD results show that the main phase of the sample is CuCrO_2 and impurities (CuCr_2O_4). From the SEM results, the average particle size is 155.948 μm .

Keyword: Delafossite, CuCrO_2 , sol-gel method.

ABSTRAK

Penelitian ini bertujuan untuk menganalisis material CuCrO_2 dengan menggunakan metode sol-gel. Karakterisasi yang digunakan adalah X-ray Diffraction (XRD) dan Scanning Electron Microscope-Energy Dispersive Spectroscopy (SEM-EDS). Pembuatan sampel dilakukan dengan cara menimbang bahan baku dan mengukur larutan dengan gelas ukur sesuai perhitungan stoikiometri, kemudian dilarutkan, dibakar, digiling, dikalsinasi, disinter, dibentuk menjadi pelet, dan disinter kembali. Hasil XRD menunjukkan bahwa fasa utama dari sampel adalah CuCrO_2 dan pengotor (CuCr_2O_4). Dari hasil SEM rata-rata ukuran partikel adalah 155,948 μm .

Kata kunci: Delafossite, CuCrO_2 , Metode sol-gel.

1. Introduction

Related studies on delafossite oxides are of interest in examining the properties of TCO and their applications as photocatalysts for hydrogen evolution [1] – [4]. AMO_2 delafossite compounds derived from the mineral CuFeO_2 are quite attractive materials because of their ability to be stabilized with a large number of A and M cations and over a wide range of off-stoichiometric values, leading to different physical properties [5] – [7].

Delafossite oxide CuRO_2 ($R^{1/4}$ trivalent cations) is one of several systems with triangular antiferromagnetic sub-lattices. CuRO_2 has a layered structure with space group R-3M, which is seen as an alternative arrangement of edge-to-edge RO 6 octahedral (RO_2) layers and a Cu layer. The magnetic properties of these layered compounds have attracted much attention since geometric frustration in the magnetic triangular *sublattice* at the R site leads to interesting properties such as field-induced multistep magnetization changes [8]. Research by Amami et al. [9] produces Al-doped CuCrO_2 material that dilutes its magnetization and screws up order antiferromagnetic. In a study conducted by Luo et al. regarding the effect of Ni doping on CuCrO_2 material, it turns out that adding Ni doping can increase characteristic ferroelectric and magnetization against CuCrO_2 [10] material.

Based on the above explanation, this study aimed to synthesize CuCrO_2 materials using the sol-gel method to obtain unique properties on the characteristics of CuCrO_2 materials.

2. Method

The materials used are Cr_2O_3 , $\text{Cu}(\text{NO}_3)_2$, $\text{CO}(\text{NH}_2)_2$, aquadest and 65% HNO_3 solution. The materials were weighed based on the compositions given in Table 1.

Table 1. Material Composition

Ingredients	Mass
Cr_2O_3	1.52 g
Aquadest	10 ml
HNO_3 65%	4.17 ml
$\text{Cu}(\text{NO}_3)_2$	4.83 g
$\text{CO}(\text{NH}_2)_2$	2.40 g

The Cr_2O_3 , $\text{Cu}(\text{NO}_3)_2$, and $\text{CO}(\text{NH}_2)_2$ were dissolved in 65% HNO_3 solution using a magnetic stirrer on a hotplate at 210 rpm. Next, the sample was heated at 90°C for 2 hours; after 2 hours, the magnetic stirrer was taken and heated for 1 hour at 200°C . Then, process the sample has turned into a gel and is then burned by inserting the sample into the furnace for 3 hours at 300°C . After this process, the sample will become powder. Next, the materials were mixed into the mortar and crushed manually for 3 hours, then calcined in a furnace with a temperature of 780°C for 3 hours, then crushed again for 3 hours. Next, the sample powder is pressed (350 MPa) into a pellet with a diameter of 10 mm and a thickness of 2 mm. Finally, the pellets were sintered again at 1000°C for 3 hours.

Furthermore, the pellets were characterized using X-ray Diffractometer (XRD) and Scanning Electron Microscopy/Energy Dispersive Spectroscopy SEM/EDS

3. Results and Discussion

3.1 XRD Analysis

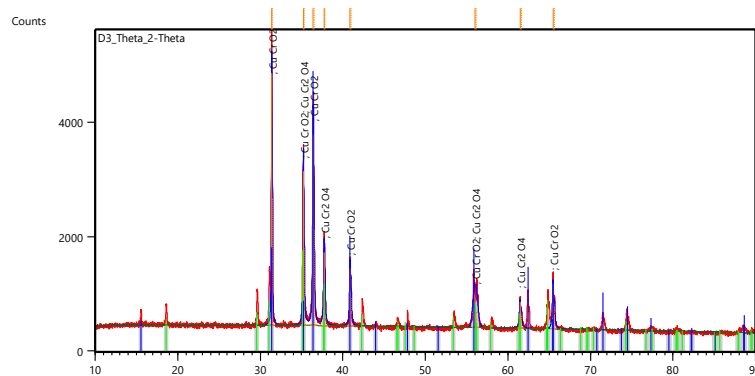


Figure 1. XRD pattern of CuCrO_2

Figure 1 shows the XRD results on the CuCrO_2 sample. XRD test was carried out to determine the formed phases. From the diffraction pattern in Figure 1, the CuCrO_2 phase is obtained as the main phase and CuCr_2O_4 phase as the impurity phase. The percentage fraction CuCrO_2 phase was 68%, and CuCr_2O_4 was 32% phase, which was analyzed using the HighScore Plus software with the database, namely COD 2021.

Table 2. Crystallite size of CuCrO_2

Peak	Bobs. [$^\circ 2\text{Th}$]	B std. [$^\circ 2\text{Th}$]	Peak post. [$^\circ 2\text{Th}$]	B struct. [$^\circ 2\text{Th}$]	Crystallite size [\AA]
1	0.049	0.008	31.397	0.041	2013
2	0.098	0.008	35.220	0.09	926
3	0.098	0.008	36.423	0.09	929
4	0.118	0.008	37.746	0.11	763
5	0.197	0.008	40.910	0.189	449
6	0.63	0.008	56.061	0.622	145
7	0.315	0.008	61.519	0.307	301
8	0.315	0.008	65.521	0.307	308
Average					729.25

Crystallite size value was calculated using the Scherer equation using HighScore plus calculator from the XRD testing data by selecting the eight highest peaks. The average size obtained crystals on CuCrO_2 samples was 729.25Å.

3.2 SEM Analysis

Characterization SEM is used to analyze the surface morphology of the CuCrO_2 , as seen in Figure 2.

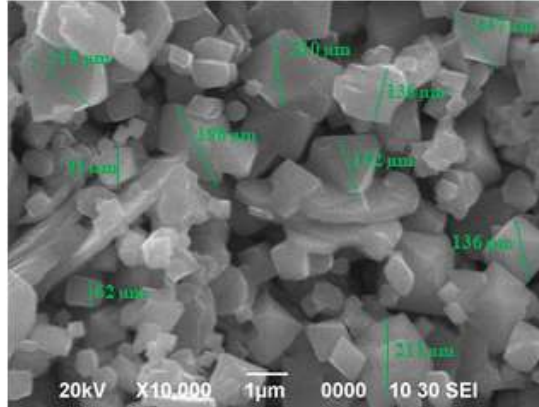


Figure 2. SEM results of CuCrO_2 samples with a magnification of 10,000 times

As seen in Figure 2, the sample has a hexagonal shape, which is distributed evenly with different sizes. The calculation of the particle size was conducted using ImageJ software, in which the average size of the sample is 155.948 μm

3.3 SEM-EDS Analysis

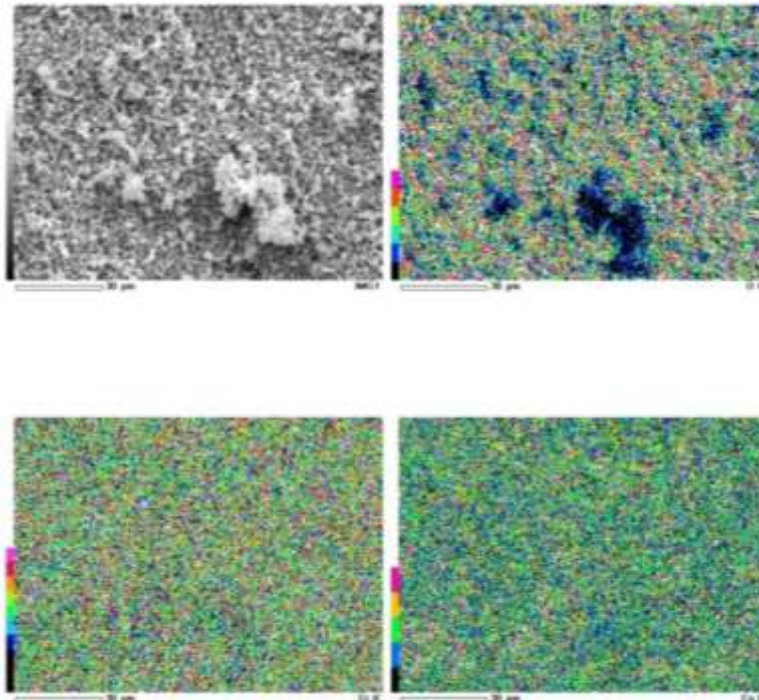


Figure 3. The elemental mapping of CuCrO_2 samples with 1000X magnification

As shown in Figure 3, the percentage of Cu and Cr mass elements was 39.47% and 42.28%, respectively, which is sufficiently high and tends to spread equally. In contrast, elemental O was 15.24% with a low mass percentage but distributed evenly.

4. Conclusion

The CuCrO_2 has been produced successfully using the sol-gel method. The XRD pattern shows that the dominant phase is the CuCrO_2 phase even though there are some impurity peaks. Particle average size on SEM testing is $155.948 \mu\text{m}$, and seen clearly on mappings SEM-EDS testing that patterns on Cu and Cr elements are distributed evenly.

5. Acknowledgments

The authors would like to thank the National Innovation Research Agency-BRIN for laboratory equipment and testing facilities and BRIN Advanced Materials Research Center researchers for their support and assistance in conducting research.

References

- [1] S. Saadi, A. Bouguelia, and M. Trari, "Photocatalytic hydrogen evolution over CuCrO_2 ," *Solar Energy*, vol. 80, no. 3, pp. 272–280. 2006.
- [2] R. Daou, R. Frésard, V. Eyert, S. Hébert, and A. Maignan, "Unconventional aspects of electronic transport in delafossite oxides," *Science and Technology of Advanced Materials*, vol. 18, no. 1, pp.919-938. 2017.
- [3] T. Okuda, N. Jufuku, S. Hidaka, and N. Terada, "Magnetic, transport, and thermoelectric properties of the delafossite oxides $\text{CuCr}_{1-x}\text{Mg}_x\text{O}_2$ ($0 \leq x \leq 0.04$)," *Physical Review B*, vol. 72, no. 14, pp. 144403. 2005
- [4] T. Elkhouni, M. Amami, C. V. Colin, P. Strobel, and A. B. Salah, "Synthesis, structural and magnetic studies of the $\text{CuCr}_{1-x}\text{CO}_x\text{O}_2$ delafossite oxide," *Journal of magnetism and magnetic materials*, vol. 330, pp. 101-105. 2013.
- [5] R. D. Shannon, D. B. Rogers, and C. T. Prewitt, "Chemistry of noble metal oxides. I. Syntheses and properties of ABO_2 delafossite compounds," *Inorganic Chemistry*, vol.10, no. 4, pp. 713-718. 1971.
- [6] D. Xiong, X. Zeng, W. Zhang, H. Wang, X. Zhao, W. Chen, and Y. B. Cheng, "Synthesis and characterization of CuAlO_2 and AgAlO_2 delafossite oxides through low-temperature hydrothermal methods," *Inorganic chemistry*, vol. 53, no. 8, pp. 4106-4116. 2014.
- [7] L. E. Smart, and E. A. Moore, *Solid state chemistry: an introduction*. Florida: CRC press, 2012.
- [8] X. Li, J. Wang, J. Zhang, Y. Li, Z. Hu, and J. Chu, "Spin-manipulated phonon dynamics during magnetic phase transitions in triangular lattice antiferromagnet $\text{CuCr}_{1-x}\text{Mg}_x\text{O}_2$ semiconductor films," *RSC advances*, vol. 6, no. 32, pp. 27136-27142. 2016.
- [9] M. Amami, C. V. Colin, P. Strobel, and A. B. Salah, "Al-doping effect on the structural and physical properties of delafossite-type oxide CuCrO_2 ," *Physica B: Condensed Matter*, vol. 406, no. 11, pp. 2182-2185. 2011.
- [10] S. Luo, L. Li, K. F. Wang, S. Z. Li, X. W. Dong, Z. B. Yan, and J. M. Liu, "Enhanced Magnetic and Ferroelectric Properties of Multiferroic CuCrO_2 by Ni-doping," *Thin Solids Films*, vol. 518, no. 24, pp. e50-e53. 2010.